



Yocom-McColl Testing Laboratories, Inc.

540 West Elk Place • Denver, Colorado 80216-1823 USA

PHONE (303) 294-0582 • FAX (303) 295-6944

EMAIL: ymccoll@ymccoll.com

Optical Fiber Diameter Analyser (OFDA 100) Micron Test Report

Pleasant Prairie Suris/Verna Carpenter
4101 N Ashton Road
Otis Orchard WA 99027 USA

Date: 08/09/16
Shear ID: 128128
Test No: 929644


Animal and Sample Description

Animal Name: Taramisu of PVA
ARI #: 32348132
Breed: Alpaca(Suri)
Sex: Female
Color: Med Brown

Date of Birth (Age): 10/14/13
Sample Location: Side
Sample Date: 06/04/16
Previous Shear Date: 06/05/15
Total Fleece Wt (lbs): 7.80

Laboratory Data

Mean Fiber Diameter:	19.8 microns	Mean Staple Length:	128.0 mm
Standard Deviation:	5.0 microns	Length Standard Deviation:	7.0 mm
Coefficient of Variation:	25.2 %	Length Coefficient of Variation:	5.4 %
Spin Fineness:	20.0 microns	Mean Curvature:	25.2 deg/mm
Fibers Greater Than 30 microns:	2.2 %	SD Curvature:	39.6 deg/mm
Comfort Factor:	97.8 %		

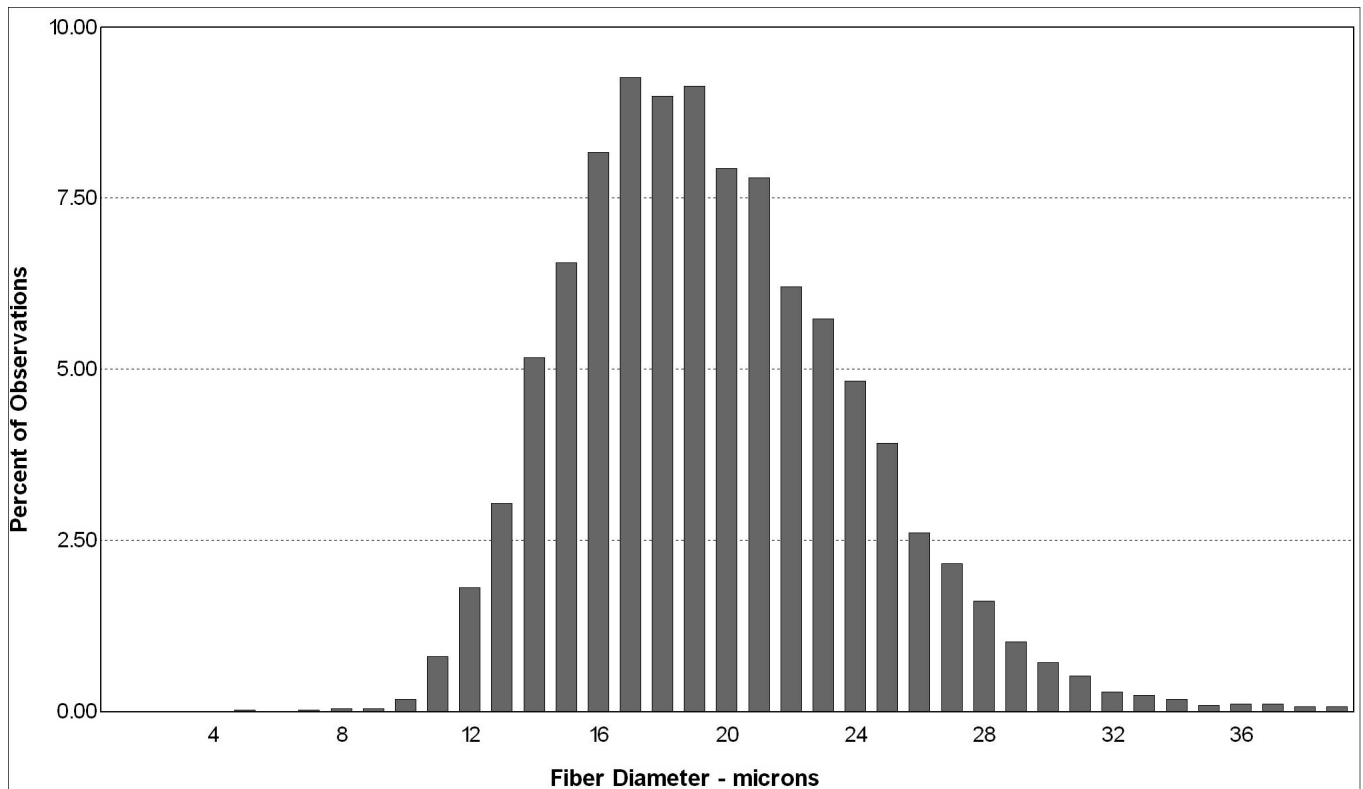

This Test Performed According to I.W.T.O Method 47